



Green Synthesis of Antimicrobial Silver Nanoparticles using Green Tea Extract: The Role of Concentration and pH

Wafiqah Latuapo Hasan, Retno Sari*, Esti Hendradi

Faculty of Pharmacy, Universitas Airlangga, Campus C UNAIR Mulyorejo, Surabaya, East Java, Indonesia

ABSTRACT: Silver nanoparticles (AgNP) have been proven effective against many microbial strains with their superior antibacterial properties, due to their nano size and large surface area that can interact directly with the bacterial structure. Green synthesis for silver nanoparticles is the process of reducing Ag^+ ions to Ag^0 using plant bioactive compounds. Green synthesis is safer, environmentally friendly, and cost-effective. *Camellia sinensis* L. (green tea) containing polyphenols that can be used as a bioreductant in the formation of silver nanoparticles. This study aims to determine the effect of various concentration of $AgNO_3$, green tea extract, and pH on the physical characteristics and antibacterial activity of silver nanoparticles. The AgNPs were evaluated by UV-Vis Spectrophotometer, Dynamic Light Scattering (DLS), SEM, and FTIR. The result demonstrated that the optimal AgNP was obtained from the $AgNO_3$ concentration of 1.5 mM with 0.003% green tea extract at pH 10 which showed the highest absorbance value of 4,420 at λ 435,3 nm, with a particle size of 47,1 nm and a PDI of 0,243. The AgNPs showed growth inhibition on *Staphylococcus aureus* and *Escherichia coli* and the antibacterial activity enhance compare to $AgNO_3$.

Keywords: silver nanoparticles; green synthesis; green tea extract; pH; antibacterial activity.

Introduction

Nanoparticles (NPs) are organic and inorganic structures with sizes ranging from 1 to 100nm, which can be obtained by physical, chemical, and recently environmentally friendly synthesis methods [1]. Recent findings show that when particles of a certain material are reduced to the nanometer scale, they will have different properties compared to the original particles which include larger surface areas (enhancing physical, chemical, and biological activity), increased solubility, and a higher level of sensitivity [2]. In the medical field, silver is a non-toxic and safe inorganic antibacterial agent that can kill about 650 types of pathogenic microorganisms, but the increasing number of bacterial strains resistant to some antibiotics has led to the development of new antibacterials [3]. Silver is frequently used as an antibacterial agent in cases of open wound infections [4]. Silver nanoparticles (AgNP) have the advantage of being small in size so that the surface area is large, leading to silver nanoparticles interacting directly with bacterial cells [5]. AgNP was also formed based on the Surface Plasmon Resonance (SPR), as the higher concentration of $AgNO_3$, green tea extract, and pH. The absorbance value increases which

indicates the amount of silver nanoparticles increases [6]. The manufacture of silver nanoparticles is often carried out using chemical method that is expensive and also uses toxic and hazardous chemicals that may have potential environmental and biological hazards. Since the physical methods provide low yields and require high energy [7]. Meanwhile, biological method is an alternative that provides an environmentally friendly way to synthesize nanoparticles. In addition, this method is characterized as economical, easy to synthesize, does not require expensive costs, harmless, and non-toxic [8]. The nanoparticle synthesis involving reducing of ions and the formation of AgNP from plant metabolite compounds, such as terpenes, flavones, ketones, aldehydes, amides, and carboxylic acid, is known as biosynthesis or green synthesis [7]. Most NPs synthesized using plant extracts exhibit sphere sizes ranging from 5 to 50 nm and superior antibacterial activity [9].

Green tea extract from the leaves of *Camellia sinensis* L has antibacterial activity due to the presence of naturally reducing polyphenolic components [10]. Green tea extract can be used as a bioreductor and stabilizer,

Article history

Received: 01 Jun 2024
Accepted: 18 Jun 2024
Published: 30 Jun 2024

Access this article



*Corresponding Author: Retno Sari

Faculty of Pharmacy, Universitas Airlangga, Campus C UNAIR Mulyorejo, Surabaya, East Java, Indonesia 60115 | Email: retno-s@ff.unair.ac.id

in the process of of AgNP formation [11]. Therefore, green tea extract replaces organic solvents and chemical compounds in aqueous media, eliminating several steps and thus reducing costs [12]. The size and shape of NPs synthesized using plant extracts can be controlled and modified by changing parameters such as pH, temperature, reaction time [13], and concentration AgNO_3 [14].

Antibacterial activity on silver nanoparticles is generally influenced by several factors including shape, size, unique chemical and physical properties, and high specific surface [15]. In this study, we fabricated silver nanoparticles using an environmentally friendly method to investigate the effect of AgNO_3 , green tea extract, and pH, then evaluate the antibacterial potential of silver nanoparticles.

Methods

Materials

Silver nitrate (AgNO_3) (Merck KgaA, Germany), green tea extract (IMATHERB BIOTECH Co., LTD), nutrient broth (Merck KgaA, Germany), sodium hydroxide (NaOH) (Merck KgaA, Germany), *Staphylococcus aureus* (ATCC 6538), *Escherichia coli* (ATCC 8739) from the Assessment Service Unit at Universitas Airlangga, Indonesia.

Green synthesis of silver nanoparticles

The synthesis of nanoparticles used AgNO_3 with concentrations of 0.5 mM, 1.0 mM, and 1.5 mM and green tea extract with concentrations of 0.001%, 0.002%, and 0.003%.

25 mL of green tea extract solution was added to 25 mL of AgNO_3 solution and stirred at 250 rpm. The pH was adjusted using 1N NaOH to obtain pH 8,9 and 10. The reaction was allowed for 1.5 h at room temperature.

Characterization of AgNPs

Spectrophotometer UV-Vis

The UV-Vis spectrophotometer (Hitachi UH5300) was used to measure the Surface Plasmon Resonance

(SPR) of the AgNP. The SPR measurement was carried out with a wavelength of 300 - 550. From the measurement, the maximum wavelength and absorbance of the AgNP solution will be obtained.

Dynamic Light Scattering (DLS)

Particle size and polydispersity index of AgNP particles were analyzed using Delsa Nano C particle analyzer (Beckman Coulter) with Dynamic Light Scattering (DLS). The average diameter and polydispersity index (PDI) were calculated by the software from the measured particle distribution.

Fourier Transform Infrared Spectroscopy (ATR-FTIR)

The analysis was carried out using (Bruker Eco-ATR) with a sample of silver nanoparticles placed in a holder to be observed in the wave number range 4000-500 cm^{-1} with a spectrum resolution of 4 cm^{-1} to determine the functional groups contained in the AgNP sample.

Scanning Electron Microscopy (SEM)

The morphology of the particle was determined using SEM (Hitachi FlexSEM). The AgNP was mounted on a carbon-coated holder, which was then inserted into a sputter coater for gold palladium plating that lasted for approximately 120 seconds. Examination was carried out using an inspect S50 type FP 2017/12 at various magnifications, with measurements taken on multiple particles.

Antibacterial activity test

Bacteria suspension preparation

The bacteria used in this evaluation were *Staphylococcus aureus* ATCC 6538 and *Escherichia coli* ATCC 8739. Suspensions of each bacterium were prepared by adding 0.9% NaCl solution. The turbidity of bacterial suspension was measured using UV-Vis spectrophotometer at λ 580 nm. The bacteria suspension can be used if the % transmittance is $25 \pm 1\%$

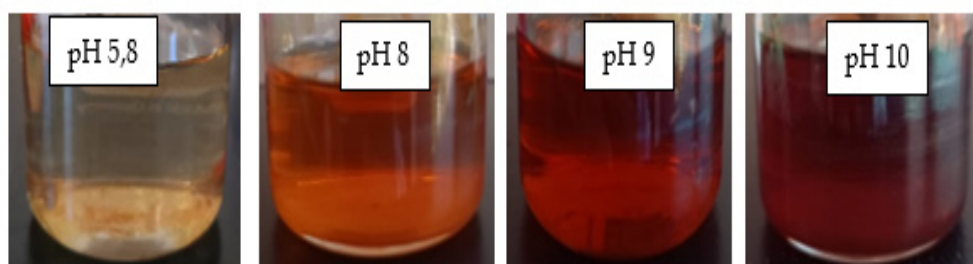


Figure 1. The color difference of AgNP at different pH

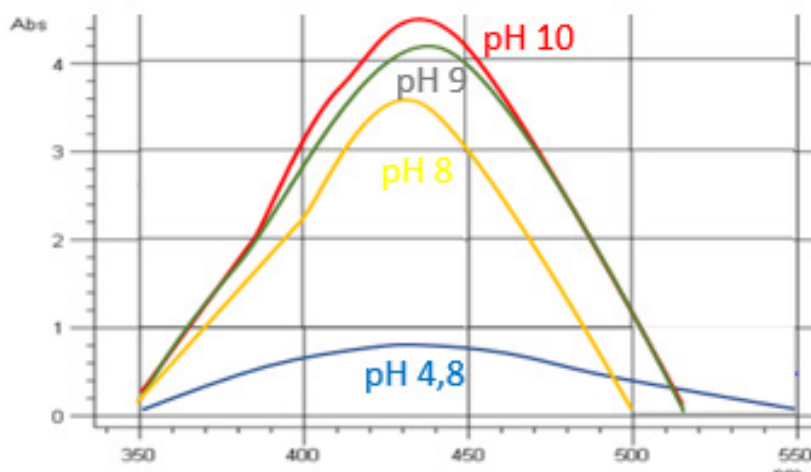


Figure 2. Absorbance spectra of AgNP with various pH at λ 350-550 nm

Antibacterial activity of AgNP

200 µl of cultured bacterial suspension in 0.9% NaCl was added into an Erlenmeyer containing 19,8ml of NB liquid media. Further AgNP solutions with the volume of 5 mL, 10 mL, 15 mL and 20 mL equivalent to 0.187 mM, 0.375 mM, 0.562 mM and 0.75 mM respectively were added into the erlenmeyer. The mixtures were shaken for 30 minutes to maximize contact between bacteria and AgNPs. Then 1 ml of each mixture was added to 9 mL of NB, then incubated at 37°C for 24 h's. The turbidity was observed by measuring the % transmittance using a UV-Vis spectrophotometer at λ 580 nm. The evaluation also performed for AgNO₃, 50 ppm Kanamycin was used as a positive control.

Result and Discussion

Synthesis of Silver Nanoparticle (AgNP) and Characterization

In this study, silver nanoparticles were synthesized

with green tea extract. The formation of AgNP can be determined by a UV-Vis spectrophotometer to observe the maximum wavelength that corresponds to the wavelength absorption of AgNP in the 400-450 nm range [16]. In green synthesis methods the formation of silver particles were observed in nanoscale with the presence of a large absorption band in the visible region. It is known that AgNPs had different colors, depending on the pH and size of AgNP [2]. The AgNPs formed were characterized by a change in the color of the solution from clear to bright yellow. Adjusting the pH of the solution causes a change in color to blackish brown (Figure 1), The color changed as the pH solution increased which indicated that AgNP had been formed and the color was the characteristics of the AgNP' Surface Plasmon Resonance (SPR) [13].

SPR depend on several factors that can affect the electron charge density on the surface of a particle, such as the type of metal, particle size, particle shape, particle structure, and dielectric constant of a medium [17]. The absorbance at a wavelength of about 400 nm indicates

Table1. Absorbance value and particle size of AgNP synthesized with various concentrations of AgNO₃, green tea extract, and pH

Observation	Variable	Green Tea Extract								
		pH 8			pH 9			pH 10		
	AgNO ₃	0.001%	0.002%	0.003%	0.001%	0.002%	0.003%	0.001%	0.002%	0.003%
Particle Size (nm)	0.5 mM	50.4	43	58	36.9	42.5	56.8	65	60.1	42.8
Absorbance		2.512	2.474	2.505	2.480	2.739	2.817	2.093	2.104	2.328
Particle Size (nm)	1 mM	80.4	69.7	66.2	46.2	51.7	77.6	38.4	37.8	35.6
Absorbance		2.798	2.921	3.006	2.969	3.393	3.388	3.561	3.485	3.917
Particle Size (nm)	1.5 mM	47	54.8	48.5	37.8	40.3	46.3	60.1	52.8	47.1
Absorbance		3.432	3.794	3.895	3.907	4.084	4.270	4.266	4.385	4.420

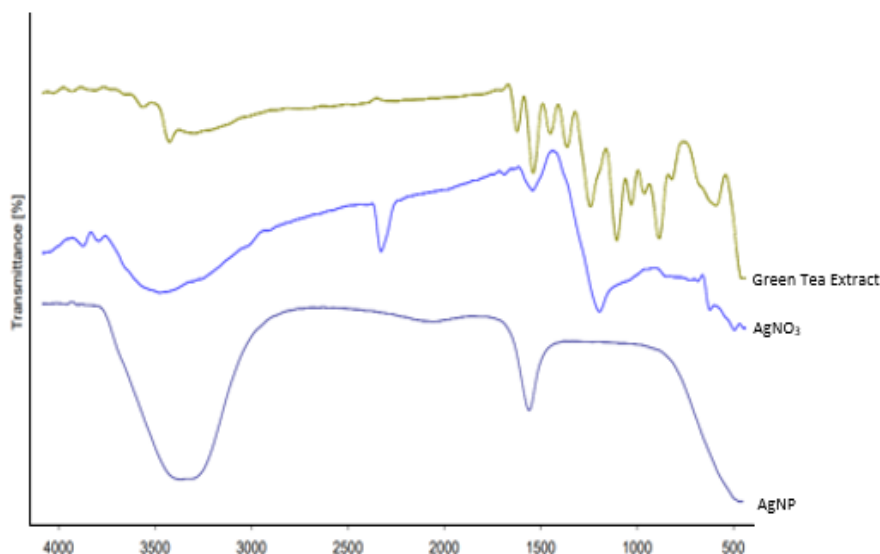


Figure 3. FTIR spectra of AgNP pH 10

the presence of silver nanoparticles formed. This can be seen in [Figure 2](#), the synthesis of AgNPs with increasing pH solution caused the absorption spectra shift towards narrower wavelength range, and the absorbance value increased, which indicated the amount of AgNP formed became higher [\[18\]](#). [Table 1](#) shows that absorbance values increased from 2.093 to 4.420 as the pH elevated from 8 to 10.

[Table 1](#) also presents the results of the evaluation using DLS to determine the particle size and particle distribution. It was known that the particle size was in the range of 35.6 nm – 80.4 nm with PDI value was 0.095 – 0.271 indicated a homogeneous particle size [\[13\]](#). PDI values close to 0 or < 0.3 indicate homogeneous particle size, while PDI value > 0.3 indicate heterogeneous particle

size [\[19\]](#). From the results, the AgNP synthesis with 1.5 mM AgNO₃, 0.003% green tea extract at pH 10 had highest absorbance value indicated higher NPAg formed compare to other condition.

The ATR-FTIR was used to determine the functional groups and chemical interactions that occur in the formation of AgNP. The results of ART-FTIR ([Figure 3](#)) showed the peak at the wavenumber 3321.30 cm⁻¹ and the hydroxyl group (-OH) presence of hydrogen bonds in AgNP [\[20\]](#). The wavenumber 2104.96 cm⁻¹ indicated that the formation of AgNP also involved stretching of symmetric and asymmetric C-H and CH aliphatic from CH₂ group. When compared with the green tea extract spectrum, there was a slight shift from 3223.38 cm⁻¹ to 3415.42 cm⁻¹. This showed the role of the phenolic group

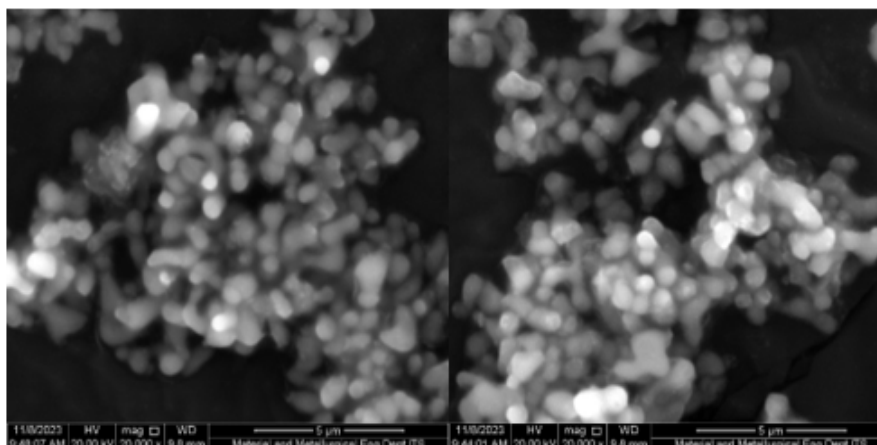


Figure 4. SEM results of AgNP with magnification 20.000x formed from a concentration of 1,5 mM AgNO₃ and 0,003% green tea extract at pH 10

Table 2. Antibacterial activity of AgNO₃ and AgNP againsts *Staphylococcus aureus* and *Escherichia coli*

Bacteria	Transmittance (%)									
	Control (+)	Control (-)	AgNO ₃ concentration (mM)				AgNP concentration (%)			
			0.187	0.375	0.562	0.75	0.187	0.375	0.562	0.75
<i>S.aureus</i>	96.17 ± 0.26	28.4 ± 0.29	34.63 ± 0.12	50.97 ± 0.25	57.30 ± 0.08	66.69 ± 0.09	75.3 ± 0.4	80.5 ± 0.031	82.2 ± 0.24	83.7 ± 0.17
	90.47 ± 0.09	30.5 ± 0.25	30.53 ± 0.12	38.37 ± 0.12	46.57 ± 0.34	57.80 ± 0.34	48.3 ± 0.08	79.6 ± 0.12	81.1 ± 0.12	82.8 ± 0.17

of the green tea extract compound in the formation of AgNP which act as reducing agent [2].


The SEM was used to determine the morphology of the particle surface. Figure 4 showed that AgNP with concentration 1.5 mM AgNO₃ and 0.003% green tea extract at pH 10 had spherical shape, irregular surface and tended to aggregate. Nanoparticles were known to be easily aggregated due to the high surface area, especially when the sample was kept in liquid form [21].

Antibacterial Activity of AgNP

The antibacterial activity was analyzed by comparing the % transmittance of AgNP with the % transmittance of AgNO₃, the positive control (Kanamycin), and the negative control. AgNPs <100 nm in size can effectively attack the bacterial cell membrane, the smaller the size of AgNPs, the easier it is to penetrate and causing toxicity the bacterial cell wall [22]. Silver ions attach to the cell wall or cytoplasmic membrane, it enhances the permeability of the cell and ultimately leads to cell disruption [23].

The results of the antibacterial activity test can be seen in Table 2 and Figure 5. The % transmittance

value of AgNP was greater compared to AgNO₃ on both bacteria tests, *Staphylococcus aureus* and *Escherichia coli*. Otherwise, the activity of AgNP against *Escherichia coli* was more concentration-dependent. The antibacterial activity of AgNPs depends on several parameters, namely particle size, particle shape, and particle surface charge [24]. Positively charged AgNP were the most effective particles and the negatively charged ones were the least effective particles against the microorganisms tested. This is due to the repulsion between bacteria and negatively charged NPAg, which can form an electrostatic barrier, thus limiting the interaction between AgNPs and bacteria [24]. This study revealed that AgNPs were more effective against gram-positive bacteria (*Staphylococcus aureus*) than to gram-negative (*Escherichia coli*). This is due to the difference of membrane and cell wall structure between gram-positive and gram-negative bacteria [25]. Gram-negative cell walls have an outer membrane, a lipopolysaccharide layer that contains polysaccharides and protein, a thicker periplasm, a gel-like matrix between the inner cytoplasmic membrane [26].

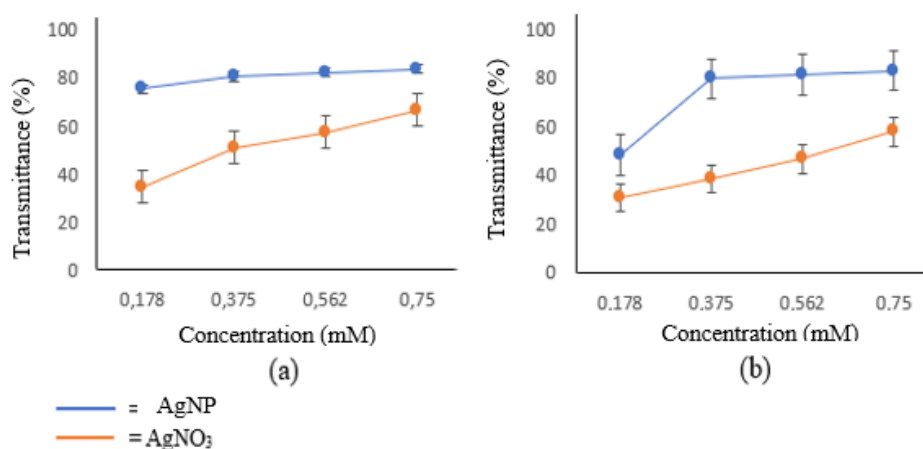**Figure 5.** The graph of antibacterial activity of AgNP and AgNO₃ against (a) *Staphylococcus aureus* (b) *Escherichia coli*

Conclusion

The formation of AgNPs is affected by AgNO₃, green tea extract concentration, and pH. AgNP obtained from 1.5 mM AgNO₃, 0.003% green tea extract and pH 10 has the smallest particles size and highest absorbance. The antibacterial activity of AgNP is higher compared to the AgNO₃ and concentration-dependent against *Escherichia coli*.

Conflict of Interest

The authors declared no conflict of interest.

Acknowledgement

The authors thank the Faculty of Pharmacy, Airlangga University for providing all facilities during the research.

References

- Bergal A, Matar GH, Andaç M. Olive and green tea leaf extracts mediated green synthesis of silver nanoparticles (AgNPs): comparison investigation on characterizations and antibacterial activity. *Bionanoscience* 2022;12. <https://doi.org/10.1007/s12668-022-00958-2>.
- Masooleh AK, Ahmadikhah A, Saidi A. Green synthesis of stable silver nanoparticles by the main reduction component of green tea (*Camellia sinensis* L.). *IET Nanobiotechnology* 2019;13:183–8. <https://doi.org/10.1049/iet-nbt.2018.5141>.
- Widatalla HA, Yassin LF, Alrasheid AA, Rahman Ahmed SA, Widdatallah MO, Eltilib SH, et al. Green synthesis of silver nanoparticles using green tea leaf extract, characterization and evaluation of antimicrobial activity. *Nanoscale Adv* 2022;4:911–5. <https://doi.org/10.1039/d1na00509j>.
- Sarheed O, Ahmed A, Shouqair D, Boateng J. Antimicrobial Dressings for Improving Wound Healing. *Wound Heal- New Insights into Anc Challenges* 2016. <https://doi.org/10.5772/63961>.
- Álvarez-Chimal R, García-Pérez VI, Álvarez-Pérez MA, Tavera-Hernández R, Reyes-Carmona L, Martínez-Hernández M, et al. Influence of the particle size on the antibacterial activity of green synthesized zinc oxide nanoparticles using *Dysphania ambrosioides* extract, supported by molecular docking analysis. *Arab J Chem* 2022;15. <https://doi.org/10.1016/j.arabjc.2022.103804>.
- Traiwatcharanon P, Timsorn K, Wongchoosuk C. Flexible room-temperature resistive humidity sensor based on silver nanoparticles. *Mater Res Express* 2017;4. <https://doi.org/10.1088/2053-1591/aa85b6>.
- Behravan M, Hossein Panahi A, Naghizadeh A, Ziaee M, Mahdavi R, Mirzapour A. Facile green synthesis of silver nanoparticles using *Berberis vulgaris* leaf and root aqueous extract and its antibacterial activity. *Int J Biol Macromol* 2019;124:148–54. <https://doi.org/10.1016/j.ijbiomac.2018.11.101>.
- Nadaroglu H, Alayli A, Nadaroglu H, Alayli Güngör A, Ince S. Synthesis of Nanoparticles by Green Synthesis Method. *Int J Innov Res Rev* 2017;1:6–9.
- Aboyewa JA, Sibuyi NRS, Meyer M, Oguntibeju OO. Green synthesis of metallic nanoparticles using some selected medicinal plants from southern africa and their biological applications. *Plants* 2021;10. <https://doi.org/10.3390/plants10091929>.
- Taylor PW, Hamilton-miller JMT, Stapleton PD. Europe PMC Funders Group Antimicrobial properties of green tea catechins. *Food Sci Technol Bull* 2009;2:71–81.
- Hasri, Iwan D, Satria PJN, Subaer. Biosynthesis of silver nanoparticles made from green tea leaf extract (*Camellia sinensis*). *Mater Sci Forum* 2019;967 MSF:161–7. <https://doi.org/10.4028/www.scientific.net/MSF.967.161>.
- Vuong Q V, Golding JB, Stathopoulos CE, Nguyen MH, Roach PD. Optimizing conditions for the extraction of catechins from green tea using hot water. *J Sep Sci* 2011;34:3099–106. <https://doi.org/10.1002/jssc.201000863>.
- Handayani W, Ningrum AS, Imawan C. The Role of pH in Synthesis Silver Nanoparticles Using *Pometia pinnata* (Matoa) Leaves Extract as Bioreductor. *J Phys Conf Ser* 2020;1428. <https://doi.org/10.1088/1742-6596/1428/1/012021>.
- Masooleh AK, Ahmadikhah A, Saidi A. Green synthesis of stable silver nanoparticles by the main reduction component of green tea (*Camellia sinensis* L.). *IET Nanobiotechnology* 2019;13:183–8. <https://doi.org/10.1049/iet-nbt.2018.5141>.
- Crisan CM, Mocan T, Manolea M, Lasca LI, Tăbăran FA, Mocan L. Review on silver nanoparticles as a novel class of antibacterial solutions. *Appl Sci* 2021;11:1–18. <https://doi.org/10.3390/app11031120>.
- Rakib-Uz-Zaman SM, Hoque Apu E, Muntasir MN, Mowna SA, Khanom MG, Jahan SS, et al. Biosynthesis of Silver Nanoparticles from *Cymbopogon citratus* Leaf Extract and Evaluation of Their Antimicrobial Properties. *Challenges* 2022;13:18. <https://doi.org/10.3390/challe13010018>.
- Huang X, El-Sayed MA. Gold nanoparticles: Optical properties and implementations in cancer diagnosis and photothermal therapy. *J Adv Res* 2010;1:13–28. <https://doi.org/10.1016/j.jare.2010.02.002>.
- Marciniak L, Nowak M, Trojanowska A, Tytkowski B, Jastrzab R. The effect of pH on the size of silver nanoparticles obtained in the reduction reaction with citric and malic acids. *Materials (Basel)* 2020;13:1–12. <https://doi.org/10.3390/ma13235444>.
- Vasconcelos AG, Valim MO, Amorim AGN, do Amaral CP, de Almeida MP, Borges TKS, et al. Cytotoxic activity of poly-ε-caprolactone lipid-core nanocapsules loaded with lycopene-rich extract from red guava (*Psidium guajava* L.) on breast cancer cells. *Food Res Int* 2020;136:109548. <https://doi.org/10.1016/j.foodres.2020.109548>.
- Samanta S, Banerjee J, Das B, Mandal J, Chatterjee S, Ali KM, et al. Antibacterial potency of cyto-compatible chitosan-decorated biogenic silver nanoparticles and molecular insights towards cell-particle interaction. *Int J Biol Macromol* 2022;219:919–39. <https://doi.org/10.1016/j.ijbiomac.2022.08.050>.
- Miranda A, Akpobolokemi T, Chung E, Ren G, Raimi-Abraham BT. pH Alteration in Plant-Mediated Green Synthesis and Its Resultant Impact on Antimicrobial Properties of Silver Nanoparticles (AgNPs). *Antibiotics* 2022;11. <https://doi.org/10.3390/antibiotics11111592>.
- Rabiee N, Ahmadi S, Akhavan O, Luque R. Silver and Gold Nanoparticles for Antimicrobial Purposes against Multi-Drug Resistance Bacteria. *Materials (Basel)* 2022;15:1–25. <https://doi.org/10.3390/ma15051799>.
- More PR, Pandit S, Filippis A De, Franci G, Mijakovic I, Galdiero M. Silver Nanoparticles: Bactericidal and Mechanistic Approach against Drug Resistant Pathogens. *Microorganisms* 2023;11. <https://doi.org/10.3390/microorganisms11020369>.
- Abbaszadegan A, Ghahramani Y, Gholami A, Hemmateenejad B, Dorostkar S, Nabavizadeh M, et al. The effect of charge at the surface of silver nanoparticles on antimicrobial activity against gram-positive and gram-negative bacteria: A preliminary study. *J Nanomater* 2015;2015. <https://doi.org/10.1155/2015/720654>.
- Tavares TD, Antunes JC, Padrão J, Ribeiro AI, Zille A, Amorim MTP, et al. Activity of specialized biomolecules against gram-positive and gram-negative bacteria. *Antibiotics* 2020;9:1–16. <https://doi.org/10.3390/antibiotics9060314>.

[26]. Matthew KF. Microbiology for Earth Scientists 2023:275.



Copyright © 2024 The author(s). You are free to share (copy and redistribute the material in any medium or format) and adapt (remix, transform, and build upon the material for any purpose, even commercially) under the following terms: Attribution — You must give appropriate credit, provide a link to the license, and indicate if changes were made. You may do so in any reasonable manner, but not in any way that suggests the licensor endorses you or your use; ShareAlike — If you remix, transform, or build upon the material, you must distribute your contributions under the same license as the original (<https://creativecommons.org/licenses/by-sa/4.0/>)